

BLM LIBRARY



88077041

RI

8533


Bureau of Mines Report of Investigations/1981

Laboratory Investigation of Sulfurous Acid Leaching of Kaolin for Preparing Alumina


By A. E. Raddatz, J. M. Gomes, and M. M. Wong

BLM Library
Denver Federal Center
Bldg. 50, OC-521
P.O. Box 25047
Denver, CO 80225

TN
23
.M57
no. 8533

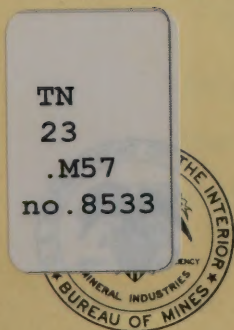

UNITED STATES DEPARTMENT OF THE INTERIOR

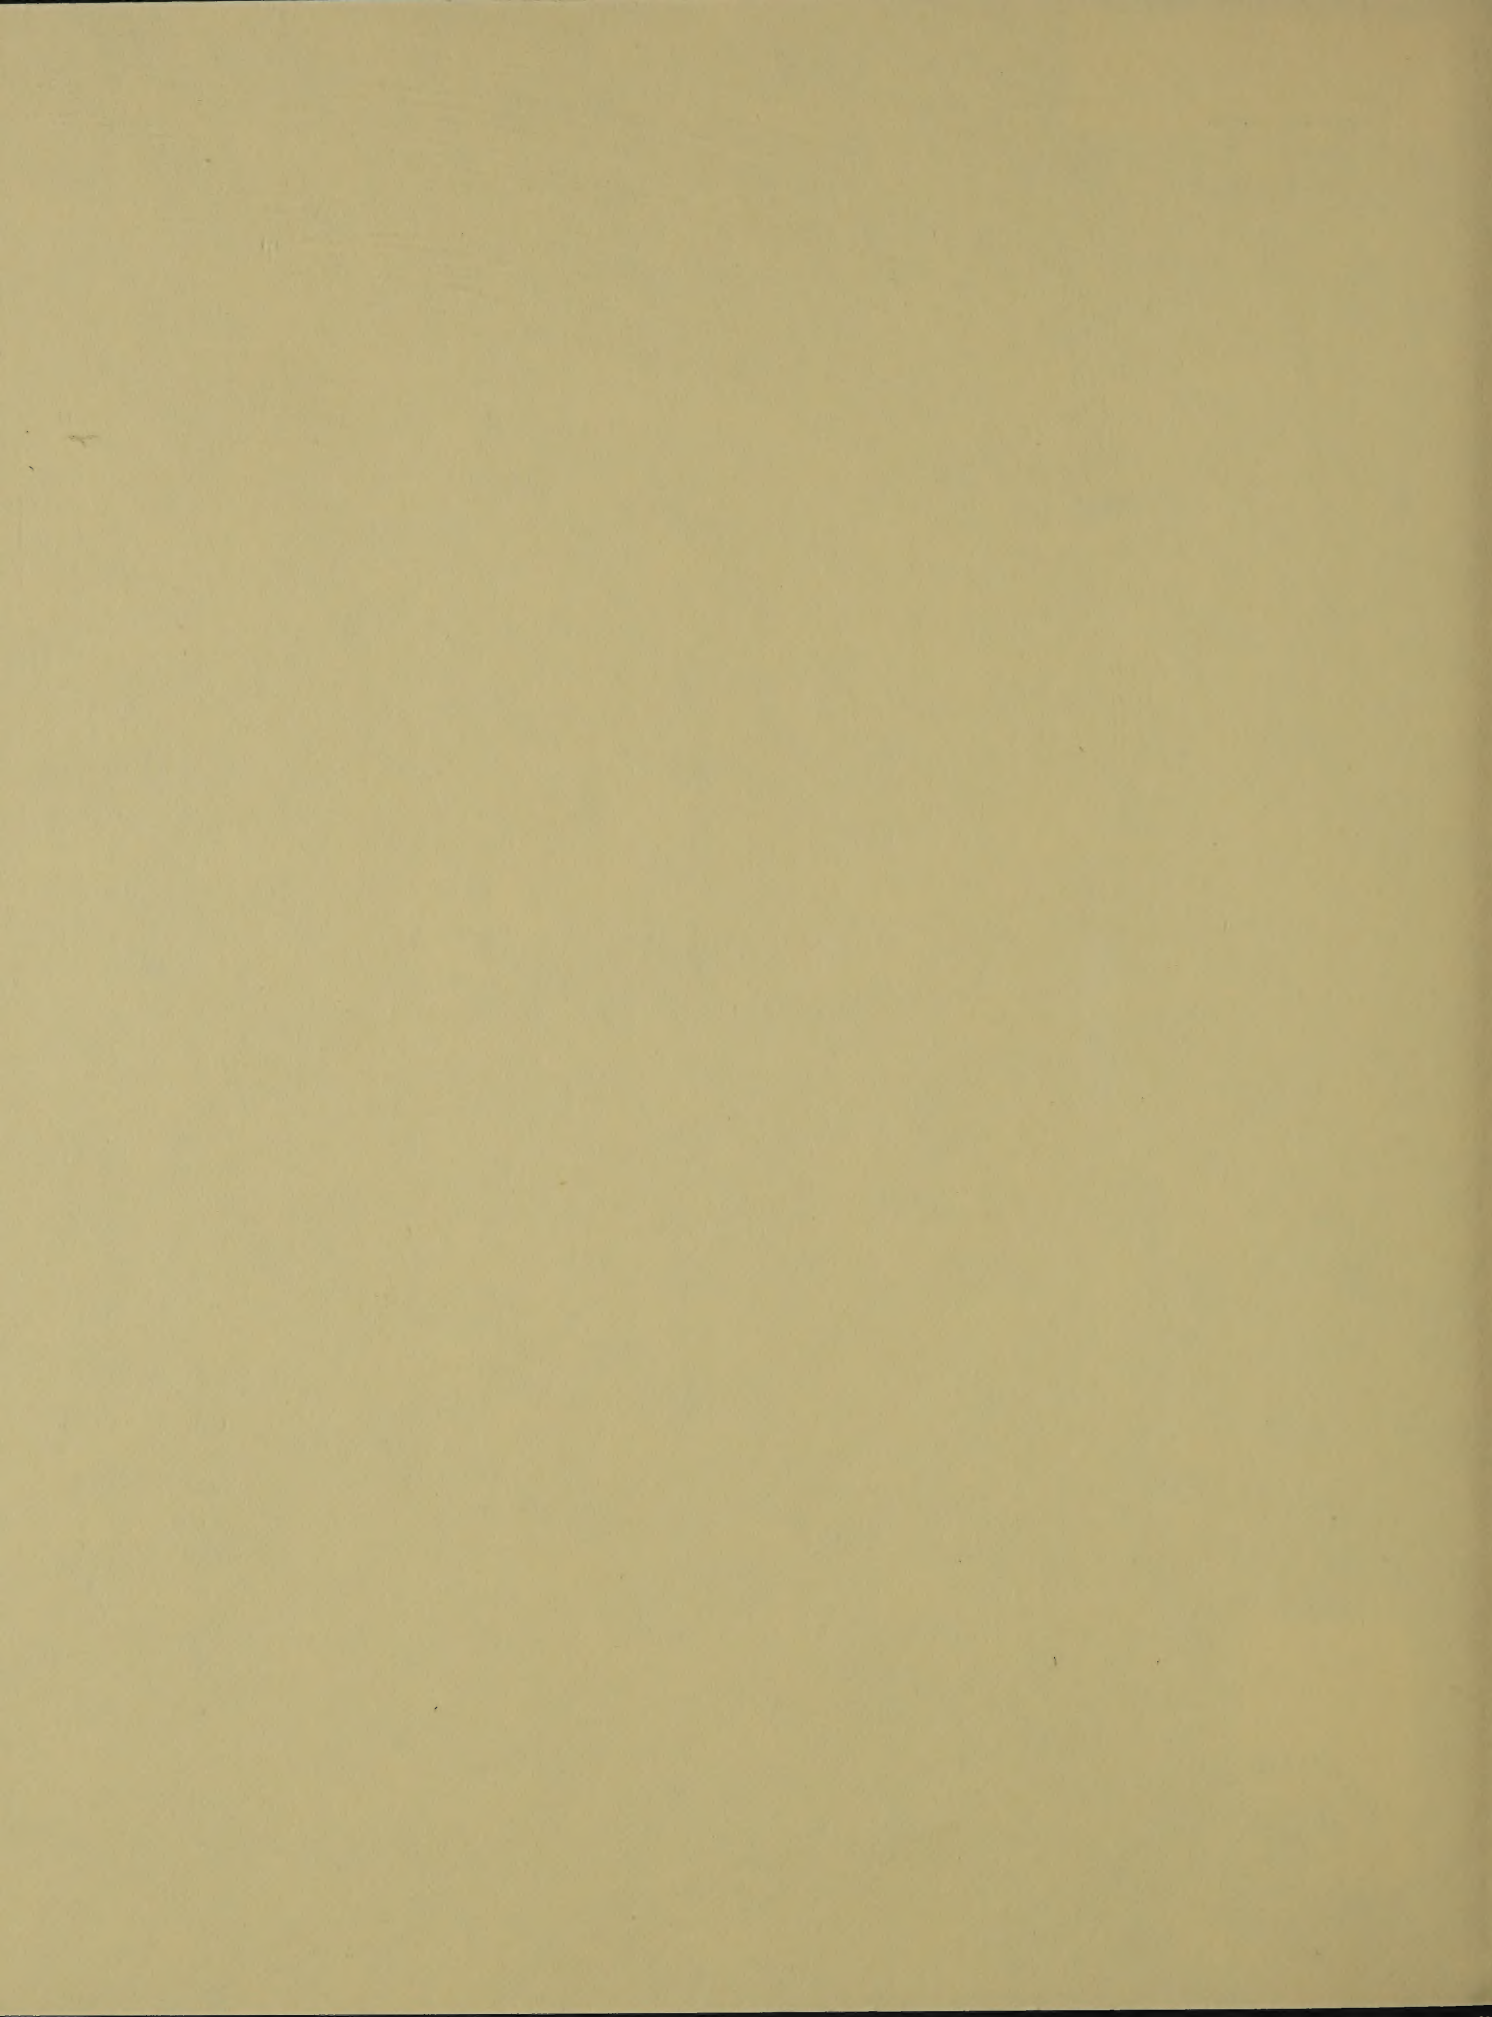

#7204669

88077041

TN
23
.M57
no. 8533

Report of Investigations 8533

Laboratory Investigation of Sulfurous Acid Leaching of Kaolin for Preparing Alumina

By A. E. Raddatz, J. M. Gomes, and M. M. Wong



UNITED STATES DEPARTMENT OF THE INTERIOR

James G. Watt, Secretary

BUREAU OF MINES

BLM Library
Denver Federal Center
Bldg. 50, OC-521
P.O. Box 25047
Denver, CO 80225

This publication has been cataloged as follows:

Raddatz, Andrea E

Laboratory investigation of sulfurous acid leaching of kaolin for preparing alumina.

(Report of investigations ; 8533)

Bibliography: p. 15.

Supt. of Docs. no.: I 28.23:8533.

1. Aluminum oxide. 2. Kaolin. 3. Leaching. 4. Sulphurous acid. I. Gomes, John M., joint author. II. Wong, Morton Min, 1924- joint author. III. Title. IV. Series: United States. Bureau of Mines. Report of investigations ; 8533.

TN23.U43 [TP245.A4] 622s [669'.722] 80-606867 • AACR1

CONTENTS

	<u>Page</u>
Abstract.....	1
Introduction.....	1
Process chemistry.....	2
Materials, equipment, and procedure.....	4
Experimental results.....	5
Leaching.....	5
Solid-liquid separation.....	6
Precipitation.....	7
Decomposition.....	8
Closed-circuit operation.....	9
Purification of crude product.....	13
Miscellaneous observations and data.....	14
Conclusions.....	14
References.....	15

ILLUSTRATIONS

1. Kaolin-sulfurous acid process with modified Bayer digestion.....	3
2. Laboratory equipment.....	4
3. Al_2O_3 extraction as a function of leach duration and temperature....	5
4. Material balance for five-cycle test.....	12

TABLES

1. Screen analysis of kaolin feed and residue.....	7
2. Analyses of leach and precipitation products.....	8
3. Effect of time on decomposition of MAS.....	9
4. Analyses of feed and intermediate products for five-cycle test.....	10
5. Distribution of major constituents in five-cycle test.....	10
6. Analyses of minor impurities in feed and intermediate products.....	11
7. Impurities in crude products.....	11
8. Analyses of feed and products from the modified Bayer purification operation.....	13
9. Impurities in calcined alumina product.....	14

CONTENTS

Page

1	Abstract
2	Introduction
3	Materials and Methods
4	Results
5	Discussion
6	Conclusions
7	References
8	Appendix
9	Tables
10	Figures
11	Summary
12	Notes
13	References
14	Appendix
15	Tables
16	Figures
17	Summary
18	Notes
19	References
20	Appendix
21	Tables
22	Figures
23	Summary
24	Notes
25	References
26	Appendix
27	Tables
28	Figures
29	Summary
30	Notes
31	References
32	Appendix
33	Tables
34	Figures
35	Summary
36	Notes
37	References
38	Appendix
39	Tables
40	Figures
41	Summary
42	Notes
43	References
44	Appendix
45	Tables
46	Figures
47	Summary
48	Notes
49	References
50	Appendix
51	Tables
52	Figures
53	Summary
54	Notes
55	References
56	Appendix
57	Tables
58	Figures
59	Summary
60	Notes
61	References
62	Appendix
63	Tables
64	Figures
65	Summary
66	Notes
67	References
68	Appendix
69	Tables
70	Figures
71	Summary
72	Notes
73	References
74	Appendix
75	Tables
76	Figures
77	Summary
78	Notes
79	References
80	Appendix
81	Tables
82	Figures
83	Summary
84	Notes
85	References
86	Appendix
87	Tables
88	Figures
89	Summary
90	Notes
91	References
92	Appendix
93	Tables
94	Figures
95	Summary
96	Notes
97	References
98	Appendix
99	Tables
100	Figures
101	Summary
102	Notes
103	References
104	Appendix
105	Tables
106	Figures
107	Summary
108	Notes
109	References
110	Appendix
111	Tables
112	Figures
113	Summary
114	Notes
115	References
116	Appendix
117	Tables
118	Figures
119	Summary
120	Notes
121	References
122	Appendix
123	Tables
124	Figures
125	Summary
126	Notes
127	References
128	Appendix
129	Tables
130	Figures
131	Summary
132	Notes
133	References
134	Appendix
135	Tables
136	Figures
137	Summary
138	Notes
139	References
140	Appendix
141	Tables
142	Figures
143	Summary
144	Notes
145	References
146	Appendix
147	Tables
148	Figures
149	Summary
150	Notes
151	References
152	Appendix
153	Tables
154	Figures
155	Summary
156	Notes
157	References
158	Appendix
159	Tables
160	Figures
161	Summary
162	Notes
163	References
164	Appendix
165	Tables
166	Figures
167	Summary
168	Notes
169	References
170	Appendix
171	Tables
172	Figures
173	Summary
174	Notes
175	References
176	Appendix
177	Tables
178	Figures
179	Summary
180	Notes
181	References
182	Appendix
183	Tables
184	Figures
185	Summary
186	Notes
187	References
188	Appendix
189	Tables
190	Figures
191	Summary
192	Notes
193	References
194	Appendix
195	Tables
196	Figures
197	Summary
198	Notes
199	References
200	Appendix
201	Tables
202	Figures
203	Summary
204	Notes
205	References
206	Appendix
207	Tables
208	Figures
209	Summary
210	Notes
211	References
212	Appendix
213	Tables
214	Figures
215	Summary
216	Notes
217	References
218	Appendix
219	Tables
220	Figures
221	Summary
222	Notes
223	References
224	Appendix
225	Tables
226	Figures
227	Summary
228	Notes
229	References
230	Appendix
231	Tables
232	Figures
233	Summary
234	Notes
235	References
236	Appendix
237	Tables
238	Figures
239	Summary
240	Notes
241	References
242	Appendix
243	Tables
244	Figures
245	Summary
246	Notes
247	References
248	Appendix
249	Tables
250	Figures
251	Summary
252	Notes
253	References
254	Appendix
255	Tables
256	Figures
257	Summary
258	Notes
259	References
260	Appendix
261	Tables
262	Figures
263	Summary
264	Notes
265	References
266	Appendix
267	Tables
268	Figures
269	Summary
270	Notes
271	References
272	Appendix
273	Tables
274	Figures
275	Summary
276	Notes
277	References
278	Appendix
279	Tables
280	Figures
281	Summary
282	Notes
283	References
284	Appendix
285	Tables
286	Figures
287	Summary
288	Notes
289	References
290	Appendix
291	Tables
292	Figures
293	Summary
294	Notes
295	References
296	Appendix
297	Tables
298	Figures
299	Summary
300	Notes
301	References
302	Appendix
303	Tables
304	Figures
305	Summary
306	Notes
307	References
308	Appendix
309	Tables
310	Figures
311	Summary
312	Notes
313	References
314	Appendix
315	Tables
316	Figures
317	Summary
318	Notes
319	References
320	Appendix
321	Tables
322	Figures
323	Summary
324	Notes
325	References
326	Appendix
327	Tables
328	Figures
329	Summary
330	Notes
331	References
332	Appendix
333	Tables
334	Figures
335	Summary
336	Notes
337	References
338	Appendix
339	Tables
340	Figures
341	Summary
342	Notes
343	References
344	Appendix
345	Tables
346	Figures
347	Summary
348	Notes
349	References
350	Appendix
351	Tables
352	Figures
353	Summary
354	Notes
355	References
356	Appendix
357	Tables
358	Figures
359	Summary
360	Notes
361	References
362	Appendix
363	Tables
364	Figures
365	Summary
366	Notes
367	References
368	Appendix
369	Tables
370	Figures
371	Summary
372	Notes
373	References
374	Appendix
375	Tables
376	Figures
377	Summary
378	Notes
379	References
380	Appendix
381	Tables
382	Figures
383	Summary
384	Notes
385	References
386	Appendix
387	Tables
388	Figures
389	Summary
390	Notes
391	References
392	Appendix
393	Tables
394	Figures
395	Summary
396	Notes
397	References
398	Appendix
399	Tables
400	Figures
401	Summary
402	Notes
403	References
404	Appendix
405	Tables
406	Figures
407	Summary
408	Notes
409	References
410	Appendix
411	Tables
412	Figures
413	Summary
414	Notes
415	References
416	Appendix
417	Tables
418	Figures
419	Summary
420	Notes
421	References
422	Appendix
423	Tables
424	Figures
425	Summary
426	Notes
427	References
428	Appendix
429	Tables
430	Figures
431	Summary
432	Notes
433	References
434	Appendix
435	Tables
436	Figures
437	Summary
438	Notes
439	References
440	Appendix
441	Tables
442	Figures
443	Summary
444	Notes
445	References
446	Appendix
447	Tables
448	Figures
449	Summary
450	Notes
451	References
452	Appendix
453	Tables
454	Figures
455	Summary
456	Notes
457	References
458	Appendix
459	Tables
460	Figures
461	Summary
462	Notes
463	References
464	Appendix
465	Tables
466	Figures
467	Summary
468	Notes
469	References
470	Appendix
471	Tables
472	Figures
473	Summary
474	Notes
475	References
476	Appendix
477	Tables
478	Figures
479	Summary
480	Notes
481	References
482	Appendix
483	Tables
484	Figures
485	Summary
486	Notes
487	References
488	Appendix
489	Tables
490	Figures
491	Summary
492	Notes
493	References
494	Appendix
495	Tables
496	Figures
497	Summary
498	Notes
499	References
500	Appendix
501	Tables
502	Figures
503	Summary
504	Notes
505	References
506	Appendix
507	Tables
508	Figures
509	Summary
510	Notes
511	References
512	Appendix
513	Tables
514	Figures
515	Summary
516	Notes
517	References
518	Appendix
519	Tables
520	Figures
521	Summary
522	Notes
523	References
524	Appendix
525	Tables
526	Figures
527	Summary
528	Notes
529	References
530	Appendix

LABORATORY INVESTIGATION OF SULFUROUS ACID LEACHING OF KAOLIN FOR PREPARING ALUMINA

by

A. E. Raddatz,¹ J. M. Gomes,² and M. M. Wong³

ABSTRACT

In an attempt to develop technology to use domestic resources in place of imported bauxite, the Bureau of Mines investigated sulfurous acid leaching to extract alumina from kaolin. The process consists of leaching the calcined kaolin with a 30 wt-pct SO_2 solution at 60°C and 160 psig for 17 hours, filtering the leach slurry, precipitating monobasic aluminum sulfite from the filtrate at 110°C and 60 psig, and decomposing the sulfite in the spent liquor at 150°C and 55 psig to produce crude alumina. Purification of the crude alumina was accomplished using a modified Bayer process.

Results from closed-circuit tests employing the sulfurous acid process showed that overall extraction of alumina from kaolin was 67 pct. Production of 1 ton of alumina would require 3.6 tons of calcined kaolin, 0.7 ton of sulfur dioxide, and 8.4 tons of water. After purification by a modified Bayer process, the alumina product contained the following impurities, expressed in weight-percent: Fe_2O_3 , 0.009; S, 3.6; SiO_2 , 0.07; TiO_2 , 0.002; K_2O , 0.017; and P_2O_5 , 0.03.

INTRODUCTION

The Bureau of Mines is conducting a program to evaluate technology for the recovery of alumina from domestic resources. Bauxite, the major alumina ore, is mainly imported. In recent years, bauxite-producing countries have formed an organization that attempts to control the supply and price of bauxite (9).⁴ The United States has only limited reserves of bauxite but has large reserves of kaolin, a clay material containing about 39 wt-pct alumina. The development of a process for the recovery of alumina from domestic resources is necessary to insure a continuing supply of alumina to meet the national needs.

¹Chemical engineer.

²Metallurgist.

³Supervisory chemical engineer.

All authors are with the Reno Research Center, Bureau of Mines, Reno, Nev.

⁴Underlined numbers in parentheses refer to items in the list of references at the end of this report.

The Bureau of Mines in cooperation with several aluminum producers has evaluated several processes for recovering alumina from domestic resources (7). The major processes studied were hydrochloric acid, nitric acid and sulfurous acid leaching of kaolin, and the lime-sinter process to treat anorthosite.

The objective of this investigation was to verify and expand the experimental data on the sulfurous acid leaching process and to determine if additional large-scale investigations in the Bureau's miniplant program were warranted.


The sulfurous acid process dates back to the late 1800's. The process development is attributed to Th. Goldschmidt A.G. which obtained numerous patents (1-5, 11-13). These patents described the different operations of the process--pretreatment and leaching of clay, precipitation of monobasic aluminum sulfite, and decomposition of the monobasic sulfite. In 1938, VAWAG at Lippewerk, Germany, tried the Goldschmidt process on a commercial scale. The alumina product recovered contained excessive quantities of impurities, such as oxides of iron, silicon, chromium, titanium, and phosphorus. A purification step similar to the Bayer process was used to produce a suitable Hall cell feed from the crude alumina. The process was described by Ginsberg and Wrigge (6). The alumina recovery was reported to be almost 80 pct. In 1962, Peters, Johnson, and Kirby made a cost evaluation of the process (10).

Interest in the sulfurous acid leaching process is due to the low cost of the SO₂ reagent, relatively easy decomposition of the monobasic aluminum sulfite, and the feasibility of substantial recovery of SO₂ offgas. The present study includes the determination of the quality of the alumina product, raw material requirements, and possible sources of environmental problems that are associated with the process.


PROCESS CHEMISTRY

The major steps of the process consist of (1) calcining kaolin at 750° C, (2) leaching the calcine in sulfurous acid (H₂SO₃), (3) separating the insoluble silica from the pregnant solution by filtration, (4) precipitating monobasic aluminum sulfite from the pregnant solution, (5) decomposing the precipitate to yield crude alumina, and (6) purifying the crude alumina by caustic digestion and reprecipitation. A flow diagram for the process sequence is shown in figure 1.

The major chemical reaction occurring in the calcining step is the dehydration of kaolin to render the alumina acid soluble,



Calcined kaolin is leached in sulfurous acid to yield aluminum sulfite and a silica residue,





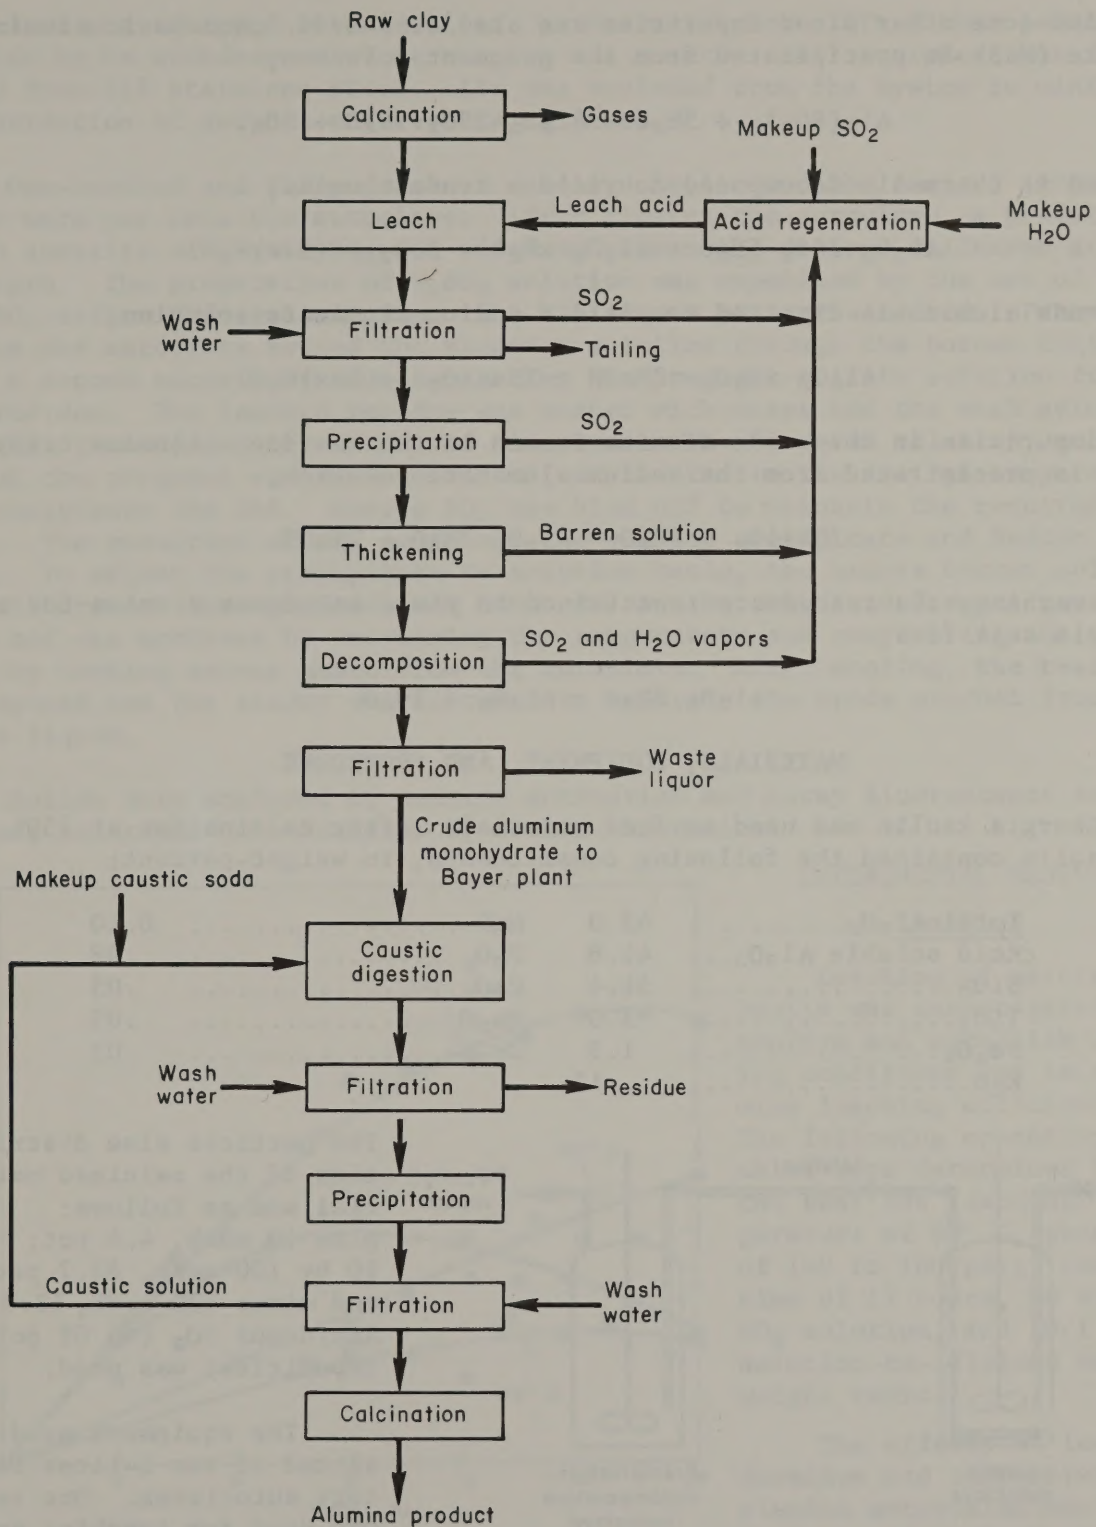


FIGURE 1. - Kaolin-sulfurous acid process with modified Bayer digestion.


Iron and some other minor impurities are also dissolved. Monobasic aluminum sulfite (MAS) is precipitated from the pregnant solution,




The MAS is thermally decomposed to yield a crude alumina,




The crude alumina is digested to yield a sodium aluminate solution,



Iron impurities in the crude alumina remain in the residue. Alumina trihydrate is precipitated from the sodium aluminate solution,



After washing, the trihydrate is calcined to yield anhydrous alumina for electrolytic cell feed,



MATERIALS, EQUIPMENT, AND PROCEDURE

Georgia kaolin was used as feed material. After calcination at 750° C, the kaolin contained the following constituents, in weight-percent:

Total Al_2O_3	43.0	MgO.....	0.10
Acid soluble Al_2O_3 ...	41.8	P_2O_508
SiO_2	51.4	CaO.....	.05
TiO_2	3.0	Na_2O05
Fe_2O_3	1.3	Cr_2O_302
K_2O11		

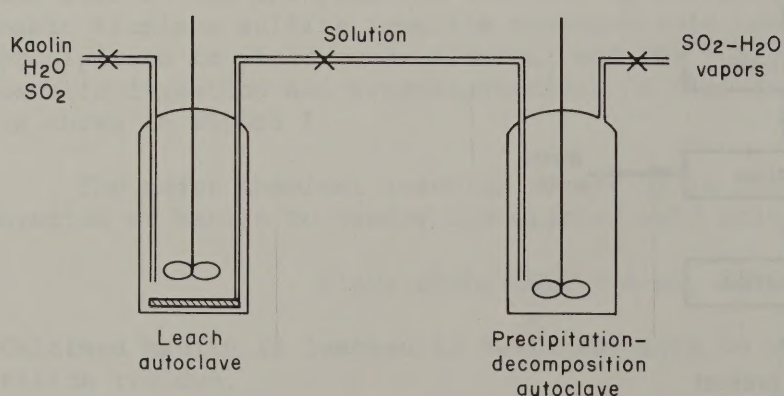


FIGURE 2. - Laboratory equipment.


The particle size distribution of the calcined material was as follows:
plus 10 mesh, 4.4 pct;
10 by 100 mesh, 82.7 pct;
and minus 100 mesh, 12.9 pct.
Anhydrous SO_2 (<0.02 pct impurities) was used.

The equipment used consisted of two 2-liter laboratory autoclaves. One vessel was used for leaching and the other for precipitation and decomposition as shown in figure 2. The leach

autoclave was equipped with a coiled, porous metal tube filter that permitted liquids to be withdrawn without opening the reactor. All equipment was fabricated from 316 stainless steel. Air was excluded from the system to minimize the oxidation of soluble sulfites to sulfates.

One-hundred and fifty grams of calcined kaolin and the desired amount of water were put into the autoclave. After closing the autoclave, a predetermined quantity of liquid SO_2 was added to obtain the desired sulfurous acid strength. The preparation of H_2SO_3 solution was expedited by the use of liquid SO_2 rather than gaseous SO_2 . The kaolin was pressure-leached. Pressure within the autoclave forced the pregnant solution through the porous tubing into a second autoclave; thus separating the pregnant sulfite solution from the residue. The leached residue was washed with water and the wash solution was then transferred to the second autoclave. The filtered solution, consisting of the pregnant and wash solutions, was heated to the desired temperature to precipitate the MAS. Excess SO_2 was bled off to maintain the required pressure. The resultant slurry contained the sulfite precipitate and barren solution. To adjust the precipitate to solution ratio, the excess barren solution was withdrawn. Decomposition was conducted in the same autoclave as precipitation and was achieved by increasing the temperature and controlling the pressure by venting excess gases from the autoclave. After cooling, the reactor was opened and the slurry was filtered to separate the crude product from the waste liquor.

Solids were analyzed by neutron activation and X-ray fluorescence techniques; solutions were analyzed by atomic absorption.

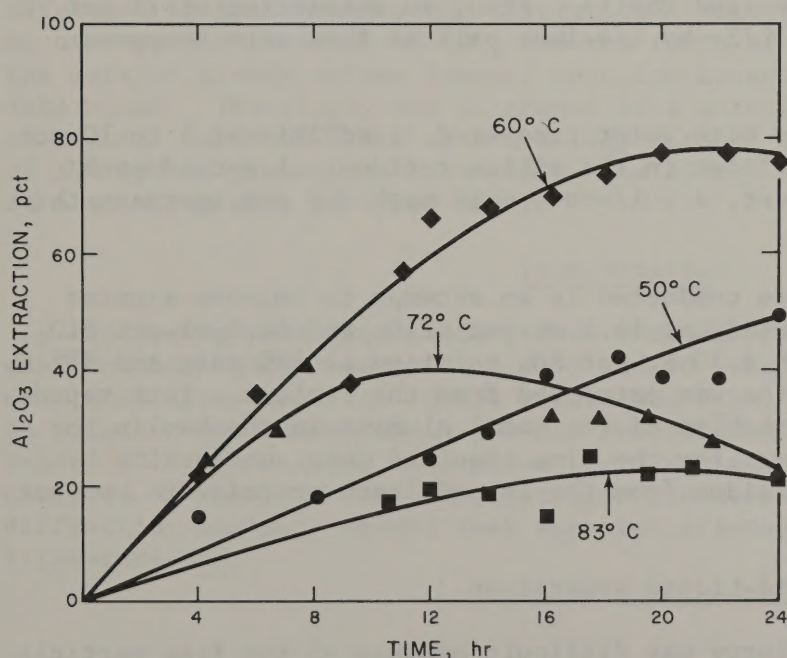

EXPERIMENTAL RESULTS

Leaching

Leaching of calcined kaolin was investigated to confirm and establish operating conditions and to determine leaching efficiencies. The following operating variables were determined to be the best for leaching: temperature of 60° C, pressure of 140 to 160 psig, leaching time of 17 hours, 30 wt-pct SO_2 solution, and 10:1 solution-to-calcined kaolin weight ratio.

The effects of leach duration and temperature on alumina extraction are shown in figure 3. Alumina extractions presented in this paper are based on total alumina in the kaolin. The best alumina

FIGURE 3. - Al_2O_3 extraction as a function of leach duration and temperature.

extraction was 80 pct and was obtained after about 20 hours of leaching at 60° C. This produced a liquor containing a maximum of 45 grams of alumina equivalent per liter. If the duration of leaching was extended beyond 20 hours, a decrease in extraction occurred. Leaching at 50° C for 24 hours resulted in an alumina extraction of about 50 pct. At 72° C, the best extraction was 40 pct in 8 hours; beyond 8 hours, the extraction decreased. At 83° C, the maximum extraction was only 22 pct after 17 hours. The decreased extraction at 50°, 72°, and 83° C probably was due to the precipitation of MAS.

Best alumina extraction was obtained by leaching with 30 wt-pct SO_2 solutions. Decreasing or increasing SO_2 content in the solution resulted in decreased alumina extraction as shown below:

<u>SO_2 concentration,</u>	<u>Al_2O_3 extraction,</u>
<u>wt-pct</u>	<u>pct</u>
14	42
30	69
42	25

Alumina extraction decreased to 25 pct when solutions containing 42 wt-pct SO_2 were used.

Although minus 10-mesh kaolin feed was used, tests showed that kaolin particle size had no serious effect on alumina extraction. Approximately 75 pct extractions were obtained with charges of 88 pct plus 100-mesh kaolin and 80 pct minus 100-mesh pulverized kaolin. Also, an extraction of 71 pct was obtained by leaching minus 1/2- by 1/4-inch pellets that were prepared from the minus 10-mesh kaolin.

Washing the silica residue with water recovered an additional 4 to 10 pct of the alumina entrained as sulfites in the silica residue. A second wash recovered another 2 pct. However, a sulfurous acid wash did not increase the alumina recovery.

Releaching experiments were conducted in an attempt to improve alumina extraction. Leach residue, containing 16.4 wt-pct Al_2O_3 and 64.0 wt-pct SiO_2 , was releached for 17 hours with a 30 wt-pct SO_2 solution at 160 psig and 58° C. Fifty-nine percent of the alumina was extracted from the residue. This represents an additional 19 pct extraction of the total alumina in the kaolin, or 87 pct overall. The low recovery for the time required does not justify releaching the residue. The residue from the second leach contained 9.3 wt-pct Al_2O_3 and 70.6 wt-pct SiO_2 .

Solid-Liquid Separation

Filtration of the leach slurry was difficult because of the fine particle size of the silica residue. Table 1 shows a screen analysis of the kaolin feed material and the leach residue. Leaching greatly decreased the particle size. Ninety-eight percent of the leach residue was minus 100 mesh. Use of pellets for leaching could minimize the filtration problems caused by the finely divided residue.

TABLE 1. - Screen analysis of kaolin feed and residue,
weight-percent

Screen size, mesh	Calcined kaolin feed	Leach residue
Plus 10.....	4.4	0.0
Minus 10 plus 20.....	28.9	.4
Minus 20 plus 35.....	25.3	.1
Minus 35 plus 48.....	11.8	.1
Minus 48 plus 65.....	9.3	.3
Minus 65 plus 100.....	7.4	1.0
Minus 100.....	12.9	98.1

Problems associated with filtration of the leach slurry were caused not only by the particle size of the silica residue but also by the precipitation of aluminum sulfites. Electron microprobe analysis of the residue indicated clusters of particles smaller than 1 μ m that contained silicon and aluminum, and other distinct crystalline particles that contained aluminum and sulfur, but no silicon. X-ray diffraction analysis of the residue indicated the precipitate was MAS. The precipitation of MAS was caused by pressure fluctuations that occurred during filtration.

The filtration rate of the hot leach slurry was 15.4 ml/cm² hr (3.8 gal/ft² hr) at a pressure differential of 100 psi. The residue contained 49 pct moisture after filtration. Filter aids and flocculants, such as diatomaceous earth, silica sand, Nalco 2330,⁵ Separan MG 200, and Guar Gum C-13, were not effective in facilitating the filtration. Settling rates were measured under an atmospheric pressure of SO₂, and the ratio of the clear solution volume to the settled slurry volume (termed solution-to-solid ratio in this report) was determined. The slurry was thickened to a solution-to-solid ratio of 2:1 from an initial ratio of 7.8:1 at a settling rate of 2.6 cm/hr. With the addition of 300 ppm of flocculant Nalco 2330, the slurry settled to a ratio of 1.8:1 at a settling rate of 1,520 cm/hr.

Precipitation

Operating conditions established for precipitation of MAS from the pregnant solution were 2 hours at 110° C and 60 psig. These are essentially the same conditions reported in the literature (12). About 94 pct of the aluminum in solution was recovered in the MAS precipitate. The pregnant solution contained 40.6 grams Al₂O₃ equivalent per liter and the barren solution, 2.9 g/l. Analyses of the leach and precipitation products are shown in table 2. X-ray diffraction analysis showed that the precipitates were MAS as reported in the literature (8).

⁵Reference to specific brands is made for identification only and does not imply endorsement by the Bureau of Mines.

TABLE 2. - Analyses of leach and precipitation products

	Al ₂ O ₃	SiO ₂	Fe ₂ O ₃	TiO ₂	Total S
Pregnant solution.....g/l..	40.6	0.2	1.03	0.03	89.2
Leach residue.....wt-pct..	16.4	64.0	0.34	3.7	3.1
Residue wash.....g/l..	7.4	0.04	0.23	0.01	15.7
Barren solution.....g/l..	2.9	0.2	1.14	0.005	6.8
MAS precipitate.....wt-pct..	28.7	0.04	0.15	0.032	19.0

Additional experiments were conducted to determine the settling rate of MAS in the barren solution. At atmospheric pressure the measured rate was 12 cm/hr. The addition of 150 ppm of Nalco 2330 flocculant increased the settling rate to 27 cm/hr and decreased the solution-to-solid wt-ratio of 7.5:1 to 0.7:1. The final solution-to-solid ratio to which the slurry settled was 0.65:1 at a settling rate of 11 cm/hr.

Decomposition

The following three procedures were investigated for the decomposition of MAS: (1) decomposing the MAS with all the barren solution present, (2) decomposing the MAS precipitate as a thickened slurry, and (3) decomposing the MAS precipitate after filtration and repulping in water.

The operating conditions for decomposing the MAS were a temperature of 140° to 160° C, pressure of 38 to 75 psig and time duration of 1 hour. The steam-saturation pressure at the decomposition temperature was used. This decreased the SO₂ concentration, thus minimizing the possibility of the reverse reaction between the SO₂ and the alumina product.

The decomposition conditions were modified because the procedure outlined in the literature (5-6) did not yield the desired results. A decrease in autoclave pressure during decomposition was the major modification. Decomposition at lower pressure resulted in crude products containing less sulfur.

X-ray diffraction of the product from all three procedures showed that major quantities of γ -AlOOH and a noncrystalline phase were present. The aluminum content of the products ranged from 26 to 33 wt-pct, silica from 0.2 to 1.0 wt-pct, and sulfur from 3.3 to 3.8 wt-pct. More than 70 pct of the sulfur was in the sulfate form; the remainder was sulfite. The product obtained from decomposition of the monobasic sulfite in barren solution was appreciably higher in silica. The iron content of all products was less than 0.1 wt-pct. No significant difference in the products obtained by the three procedures was observed. The recommended procedure is the decomposition of MAS precipitate in a thickened slurry that would allow approximately 50 pct of the barren solution to be recycled to the leach solution.

Results from studies to determine the effect of decomposition time are presented in table 3. The results show that decomposition times greater than 1 hour incurred a significant increase in sulfur content in the decomposition products. Other impurities remained at about the same level. A decomposition time of 0.5 hour resulted in incomplete decomposition of the MAS. The Al₂O₃

content of the product decreased with time, and the water of hydration increased. The decomposition product was filtered from the waste liquor at a rate of 69 ml/cm² hr (17 gal/ft² hr).

TABLE 3. - Effect of time on decomposition of MAS

Time, hr	Analysis of crude product, wt-pct				
	Al ₂ O ₃	SiO ₂	Total S	SO ₃ ⁼	SO ₄ ⁼
0.5.....	64.5	0.19	3.7	9.2	0.08
1.0.....	62.4	.66	3.3	2.1	7.1
1.5.....	61.2	.71	4.0	2.5	9.1
2.0.....	55.2	.45	5.1	1.3	13.8
3.0.....	48.2	.77	4.0	1.6	10.0

Closed-Circuit Operation

A bench-scale, closed-circuit operation was conducted for five cycles of leaching, precipitation, and decomposition to determine the feasibility of recycling solution, the effect of impurity buildup on the products, and the distribution of major constituents.

The operating procedure was as follows: One hundred and fifty grams of calcined kaolin and 1,500 grams of acid, composed of barren solution recycled from the previous run and additions of makeup SO₂ and water, were reacted at 62° C and 170 psig for 18 hours. The leach slurry was filtered in a closed system using a porous 316 stainless steel filter. The silica residue was washed with 500 ml of water, which was added to the pregnant solution. Conditions for precipitation were as follows: temperature, 110° C; pressure, 60 psig; and time, 2 hours. After precipitation was completed, approximately one-half of the barren solution was withdrawn and used as leach solution for the next run. Decomposition of MAS was performed under the following conditions: temperature, 145° C; pressure, 50 psig; and time, 1 hour. Vapors given off during filtration, precipitation, and decomposition were collected in a Dry Ice-cooled autoclave and analyzed by gas chromatography. No attempt was made to recycle the gases.

Analyses of the feed and intermediate products obtained in the five-cycle experiment are given in table 4. Distribution of the major constituents is shown in table 5. Alumina extraction averaged 65.8 pct. Alumina concentration decreased from 37.1 g/l in the pregnant solution to 1.6 g/l in the barren solution. The alumina concentration was <0.07 g/l in the waste liquor. Sulfur dioxide concentration in the leach solution was 321 g/l, of which 49.0 pct was bled off during filtration, an additional 30.5 pct was evolved during precipitation and finally, 10.3 pct was given off during decomposition. Concentration of SO₂ in the barren solution was 34.7 g/l and 2.3 g/l in the waste liquor. About 0.1 pct of the SO₂ was discharged in the waste liquor.

TABLE 4. - Analyses of feed and intermediate products for five-cycle test

Product	Al ₂ O ₃	SiO ₂	Fe ₂ O ₃	SO ₂
Calcined kaolin.....wt-pct..	39.1	54.5	1.23	-
Pregnant solution.....g/l..	37.1	0.4	1.35	163.2
Residue wash.....g/l..	6.3	0.3	0.3	29.5
Residue.....wt-pct..	16.0	68.4	0.56	1.2
Barren solution.....g/l..	1.6	0.9	1.1	34.7
Waste liquor.....g/l..	<0.07	0.07	1.3	2.3
Crude product.....wt-pct..	67.2	0.3	1.1	3.7

TABLE 5. - Distribution of major constituents in five-cycle test, percent

	Al ₂ O ₃	SiO ₂	Fe ₂ O ₃	SO ₂	H ₂ O
Input:					
Calcined kaolin.....	98.3	99.4	72.7	-	-
Barren solution.....	1.7	.6	27.3	4.5	44.7
SO ₂	-	-	-	95.5	-
Water, leach.....	-	-	-	-	33.5
Water, wash.....	-	-	-	-	21.8
Total.....	100.0	100.0	100.0	100.0	100.0
Output:					
Residue.....	32.5	99.1	32.8	.3	6.6
SO ₂ filtration.....	-	-	-	49.0	-
SO ₂ precipitation....	-	-	-	30.5	-
Barren solution.....	1.7	.6	27.3	4.5	44.7
Decomposition vapors.	-	-	-	10.3	25.5
Waste liquor.....	<.03	.02	14.1	.1	15.8
Crude product.....	65.8	.2	25.8	.4	7.3
Total.....	100.0	99.9	100.0	95.1	99.9

During leaching, 67.2 pct of the iron was dissolved, and 27.3 pct remained in the barren solution after precipitation. The crude product contained 1.1 wt-pct iron, which represented 25.8 pct of the iron in the kaolin, and 0.2 wt-pct silica. The crude product contained 71.8 wt-pct water after filtration and 11 wt-pct after drying. A material balance based on five cycles of integrated operation is shown in figure 4. Impurities present in the feed material and the intermediate products are shown in table 6. Impurity contents in the crude products from five cycles of operation are shown in table 7. Iron oxide was the only impurity progressively increasing during the five cycles. The total sulfur content ranged from 3.1 to 4.1 wt-pct, which included 1.6 to 2.7 wt-pct sulfur as sulfate, and 1.1 to 2.1 wt-pct sulfur as sulfite. No elemental sulfur was present. The contents of the other impurities remained approximately constant.

TABLE 6. - Analyses of minor impurities in feed and intermediate products

	CaO	Cr ₂ O ₃	K ₂ O	MgO	MnO	Na ₂ O
Kaolin.....wt-pct..	0.021	0.01	0.12	0.055	0.009	0.030
Pregnant solution.....g/l..	0.025	<0.012	0.13	0.083	0.014	0.030
Residue wash.....g/l..	0.003	<0.012	0.033	0.010	0.003	0.009
Residue.....wt-pct..	0.017	<0.01	0.11	0.028	0.004	0.032
Barren solution.....g/l..	0.022	<0.012	0.104	0.066	0.011	0.027
Waste liquor.....g/l..	0.036	<0.012	0.17	0.14	0.016	0.045
Crude product.....wt-pct..	0.006	0.02	0.017	0.007	0.002	0.027
	NiO	P ₂ O ₅	PbO	TiO ₂	ZnO	ZrO ₂
Kaolin.....wt-pct..	0.004	0.065	0.011	3.02	0.005	0.050
Pregnant solution.....g/l..	0.014	0.073	<0.009	<0.08	0.006	<0.007
Residue wash.....g/l..	0.004	0.006	<0.009	<0.08	0.001	<0.01
Residue.....wt-pct..	0.002	0.029	0.006	3.45	0.003	0.065
Barren solution.....g/l..	0.008	0.004	<0.009	<0.08	0.001	<0.007
Waste liquor.....g/l..	<0.003	0.001	<0.009	<0.08	0.001	<0.007
Crude product.....wt-pct..	0.008	0.120	0.014	0.05	0.006	0.006

TABLE 7. - Impurities in crude products, weight-percent

	Cycle 1	Cycle 2	Cycle 3	Cycle 4	Cycle 5
CaO.....	0.006	0.020	0.007	0.008	0.002
Fe ₂ O ₃37	.89	.74	.87	1.13
K ₂ O.....	.024	.083	.017	.063	.017
MgO.....	.009	.010	.006	.007	.009
MnO.....	.002	.003	.002	.004	.005
Na ₂ O.....	.027	.015	.027	.018	.019
NiO.....	.006	.008	.008	.009	.008
P ₂ O ₅12	.15	.13	.13	.15
PbO.....	.008	.008	.007	.014	.014
Total sulfur.....	4.1	3.5	3.5	3.7	3.1
SiO ₂	<.2	.2	.2	<.2	.6
TiO ₂053	.046	.046	.050	.054
ZnO.....	.006	.010	.010	.010	.010
ZrO ₂006	.007	.006	.006	.007

Sulfur dioxide consumption per pound of alumina recovered was 0.7 pound. Less than 6 pct of the total SO₂ used in the process was consumed or lost, while about 94 pct was available for recycle. About 0.8 pct of the SO₂ was lost in the residue, waste liquor, and crude product. About 70 pct of the sulfur contamination in the crude product was present as sulfate; the remainder was sulfites. Sulfur is multivalent and easily oxidized from sulfite to sulfate in solution. Sulfur dioxide was not reduced to elemental sulfur. Sulfur dioxide losses caused by leakage from the equipment amounted to 4.9 pct. Escape of SO₂ and disposal of liquid and solid wastes may present difficult environmental problems.

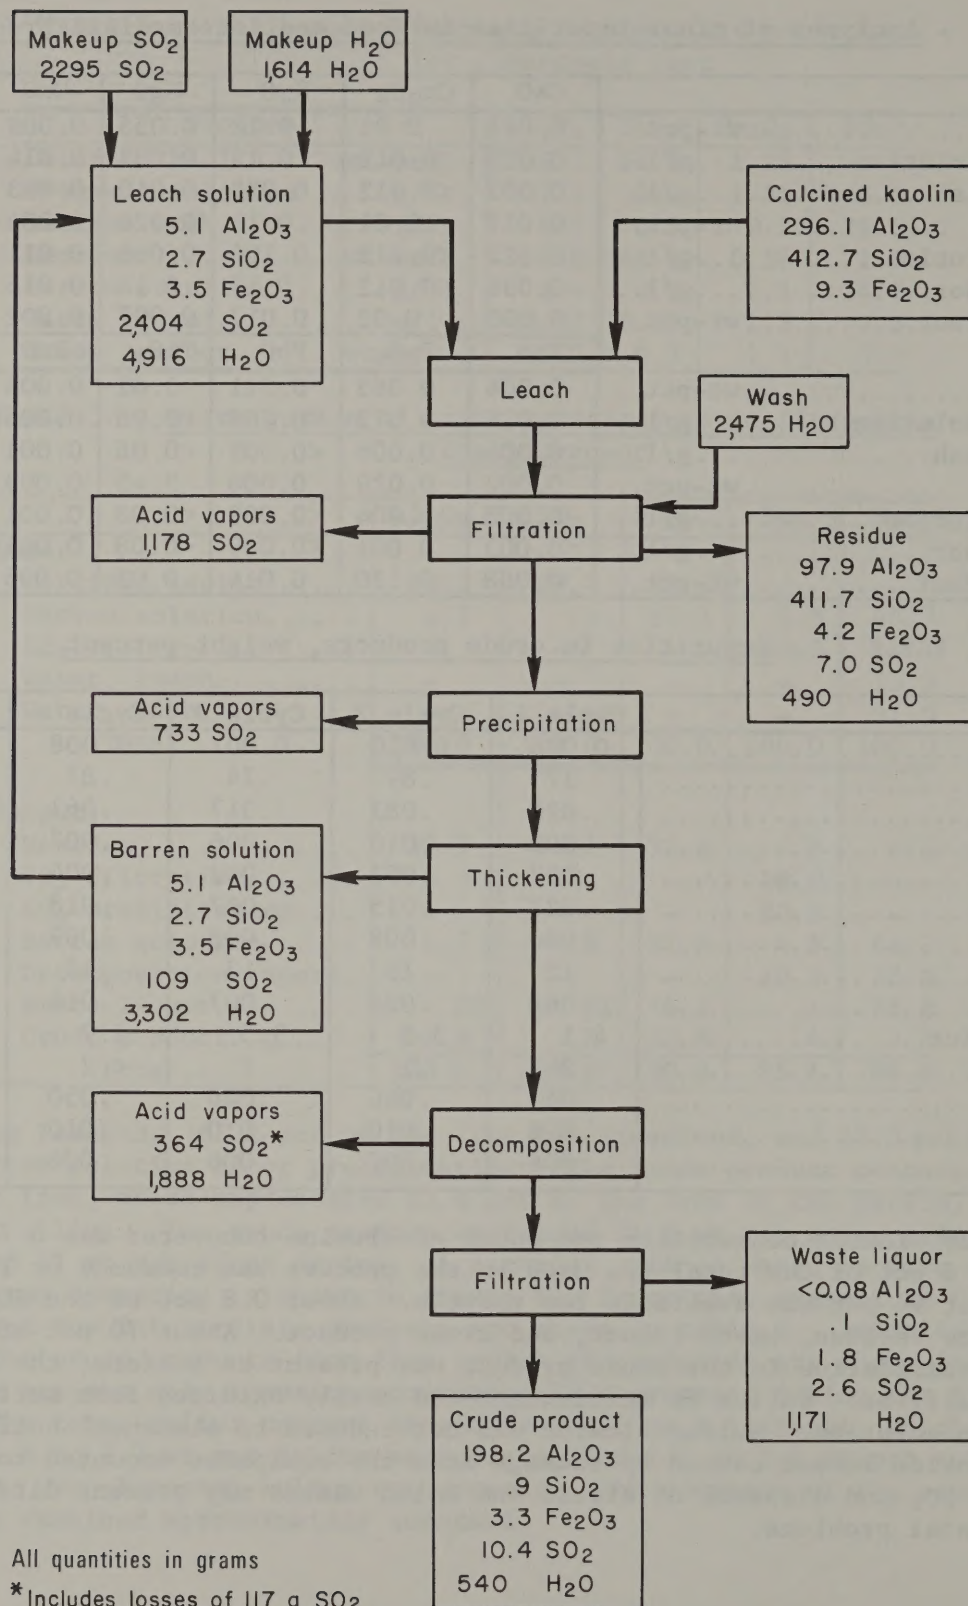


FIGURE 4. - Material balance for five-cycle test.

Analysis of the offgases collected during filtration and precipitation showed SO_2 and no water vapor. The detection limit for water was less than 0.1 pct. Gases given off during decomposition contained from 6 to 16 wt-pct SO_2 and 84 to 94 wt-pct water.

Purification of Crude Product

A modified Bayer digestion was necessary to remove excessive quantities of impurities, such as silica and iron, from the crude product from the decomposition of MAS. The purification was required to produce an acceptable cell feed for electrolytic reduction. Because the Bayer process is well known, this phase of the process received only a cursory investigation.

Only 75 pct of the alumina was extracted using an atmospheric leach at 90° C. The decomposition product, identified by X-ray diffraction analysis as aluminum monohydrate, requires higher temperatures and pressures for digestion.

The crude products obtained from the five-cycle operation were combined for use in the purification test. The crude product was dissolved in a caustic solution containing 373 grams of NaOH/l . Digestion required a temperature of 250° C, pressures up to 500 psig, and time of 2 hours. Ninety-eight percent of the alumina contained in the decomposition product was dissolved. After filtration to separate the insoluble residue from the liquor, the liquor was cooled to 50° C and seeded with aluminum trihydrate. A hydrolyzed precipitate was obtained and identified by X-ray diffraction as gibbsite, $\alpha\text{-Al}(\text{OH})_3$, and bayerite, $\beta\text{-Al}(\text{OH})_3$. The precipitate was calcined at 1,200° C. The calcined alumina was identified as $\beta\text{-Al}_2\text{O}_3$ by X-ray diffraction analysis.

Analyses of the crude feed, the digestion residue, and the calcined product are shown in table 8. Sulfur in the calcined alumina product reached 3.6 wt-pct, which is probably higher than acceptable for electrolytic cell feed. Maximum sulfur specifications are not available from alumina producers. Other impurities are listed in table 9 and are compared with the generally accepted values for cell-grade alumina. The product exceeds the target values for Cr_2O_3 , K_2O , P_2O_5 , and SiO_2 . The results indicate that the alumina obtained was not a suitable feed for reduction cells.

TABLE 8. - Analyses of feed and products from the modified Bayer purification operation, weight-percent

	Al_2O_3	SiO_2	Fe_2O_3	TiO_2	Total S
Crude feed.....	67.2	0.3	1.1	0.05	3.6
Residue.....	20.8	13.4	34.6	1.5	1.1
Calcine.....	65.6	.07	.009	.002	3.6

TABLE 9. - Impurities in calcined alumina product,
weight-percent

Component	Target value ¹	Calcined product
CaO.....	0.05	0.006
Cr ₂ O ₃002	<.015
Fe ₂ O ₃025	.009
K ₂ O.....	.005	.017
MgO.....	.002	<.001
MnO.....	.001	<.0008
NiO.....	.005	.0006
P ₂ O ₅003	.03
SiO ₂025	.07
TiO ₂005	.002
ZnO.....	.019	.012

¹Compiled from Alumina Miniplant Steering Committee
1974 and Encyclopedia of Chemical Technology,
3d ed., v. 2, 1978, p. 143.

Miscellaneous Observations and Data

Throughout these tests, 316 stainless steel withstood severe conditions of SO₂ concentrations up to 30 wt-pct and temperatures up to 150° C. Corrosion did occur on components in contact with solutions containing more than 15 wt-pct SO₂ and temperatures in excess of 160° C. In these incidents, X-ray fluorescence scan indicated iron, chromium, and nickel present in the leach solution.

CONCLUSIONS

Sulfurous acid leaching of calcined kaolin with a caustic purification does not produce alumina that meets cell feed specifications for alumina purity. A major contaminant is sulfur, which is not decreased by caustic purification. The process requires long leach duration and yields low alumina extraction. Escape of SO₂ because of leakages in pressurized equipment presents an environmental problem. Sulfites and sulfurous acid present in the waste liquor require treatment to render the solution innocuous before disposal. For these reasons, the Bureau has concluded that larger scale investigations of the sulfurous acid leaching process, under its cooperative miniplant program, are not warranted.

REFERENCES

1. Buche, K., and H. Ginsberg (assigned to Goldschmidt Corp., New York). Solubilizing Claylike Minerals. U.S. Pat. 2,267,490, Dec. 23, 1942.
2. Fulda, W., E. Wiedbrauck, and K. Buche (assigned to Th. Goldschmidt A.G., Essen, Germany). Process for the Recovery of Aluminum Compounds From Aluminiferous Minerals. U.S. Pat. 2,123,650, July 12, 1938.
3. _____. (Assigned to Goldschmidt Corp., New York). Manufacture of Monobasic Aluminum Sulphite. U.S. Pat. 2,243,060, May 20, 1941.
4. Fulda, W., E. Wiedbrauck, and R. Wittig (assigned to Vereiniget Aluminum-Werke A.G., Lusatia, East Germany, and Th. Goldschmidt A.G., Essen, Germany). Methods of Producing Pure Alumina. U.S. Pat. 2,021,546, Nov. 19, 1935.
5. Fulda, W., W. Wrigge, and H. Logemann (assigned to Goldschmidt Corp., New York). Separating Sulphurous Acid From Aluminum Sulphites. U.S. Pat. 2,261,113, Nov. 4, 1941.
6. Ginsberg, H., and F. W. Wrigge. Alumina and Aluminum (Tonerde und Aluminum Die Tonerde). Walter DeGruyter and Co., Berlin, Germany, v. 1, 1964, pp. 156-166.
7. Kirby, R. C., and A. S. Prokopovitch. Technological Insurance Against Shortages in Minerals and Metals. Science, v. 191, Feb. 20, 1976, pp. 713-719.
8. Ko, H. C., J. M. Stuve, and R. R. Brown. Enthalpy of Formation and Low-Temperature Heat Capacities of Basic Aluminum Sulfite ($\text{Al}_2\text{O}_3 \cdot 2.0 \text{ SO}_2 \cdot 5.3 \text{ H}_2\text{O}$). BuMines RI 8164, 1976, 13 pp.
9. Kurtz, H. F. Bauxite. BuMines Mineral Commodity Summaries 1980. P. 19.
10. Peters, F. A., P. W. Johnson, and R. C. Kirby. Methods for Producing Alumina From Clay: An Evaluation of the Sulfurous Acid-Caustic Purification Process. BuMines RI 5997, 1962, 21 pp.
11. Staufer, R., and K. Konopicky (assigned to Alterra A.G., Luxembourg). Process for Treating Argillaceous Material. U.S. Pat. 1,956,139, Apr. 24, 1934.
12. Wiedbrauck, E., and K. Buche (assigned to Th. Goldschmidt A.G., Essen, Germany). Process for the Production of Monobasic Aluminum Sulphite. U.S. Pat. 1,971,668, Aug. 28, 1934.
13. _____. (Assigned to Th. Goldschmidt A.G., Essen, Germany). Process for the Decomposition of Siliceous Aluminous Minerals. U.S. Pat. 2,006,851, July 24, 1935.

BLM Library
Denver Federal Center
Bldg. 50, OC-521
P.O. Box 25047
Denver, CO 80225

BLM Library
Denver Federal Center
Bldg. 50, OC-521
P.O. Box 25047
Denver, CO 80225

